

Hydrothermal Synthesis of Terbium doped Antimony Selenide Nanomaterials and Investigation of Their Photocatalytic Performance

Younes Hanifehpour ^{✉1} | Negin Rahmani ² | Sang Woo Joo ^{✉3}

1. Correspond author, Department of Chemistry, Sayyed Jamaledin Asadabadi University, Asadabad, Iran. E-Mail: younes.hanifehpour@gmail.com
2. Department of Chemistry, Sayyed Jamaledin Asadabadi University, Asadabad, Iran. E-Mail: rahmani.negin2004@gmail.com
3. Correspond author, School of Mechanical Engineering, Yeungnam University, Gyeongsan 712-749, Korea. E-Mail: swjoo1@gmail.com

Article Info

Article type:

Research Article

Article history:

Received 28 Sep 2023

Received in revised form 3
Jan 2024

Accepted 7 Feb 2024

Published online 27 Mar
2024

Keywords:

Terbium,
Rhodamine B,
Hydrothermal,
Semiconductor,
Photocatalyst.

ABSTRACT

Tb³⁺-doped antimony selenide nanomaterials were prepared via a hydrothermal route through the co-reduction method. The obtained products were characterized utilizing Scanning electron microscopy (SEM), X-ray photoelectron spectroscopy (XPS), transmission electron microscopy (TEM) and X-ray powder diffraction (XRPD). Powder XRD patterns indicate that the Tb_xSb_{2-x}Se₃ crystals (x = 0.00-0.1) are isostructural with Sb₂Se₃. SEM images show that doping of Tb³⁺ ions in the lattice of Sb₂Se₃ results in nanoparticles. The electrical conductance of terbium-doped antimony selenide is higher than undoped Sb₂Se₃ and increases with temperature. The synthesized nanomaterials were used as heterogeneous photocatalysts for the degradation of some water pollutant organic dyes under direct visible (with fluorescent light with 40 W Power). Rhodamine B (RB) was used as a typical dye to obtain the optimum photocatalytic degradation conditions. The photocatalytic reaction yield was 76% at the present conditions. The influence of radical scavengers on degradation percentage was investigated.

Cite this article: Hanifehpour, Y. Rahmani, N. & Woo Joo, S. (2024). Hydrothermal Synthesis of Terbium doped Antimony Selenide Nanomaterials and Investigation of Their Photocatalytic Performance, *Advances in Energy and Materials Research*, 1 (1), 23-28. <https://doi.org/10.22091/JAEM.2023.9656.1005>

© The Author(s).

Publisher: University of Qom.

DOI: <https://doi.org/10.22091/JAEM.2023.9656.1005>

The EDX analysis of the product confirms the ratio of Sb/Se/Tb as expected (see Figure 2). Also, ICP analysis confirms the exact amount of doping.

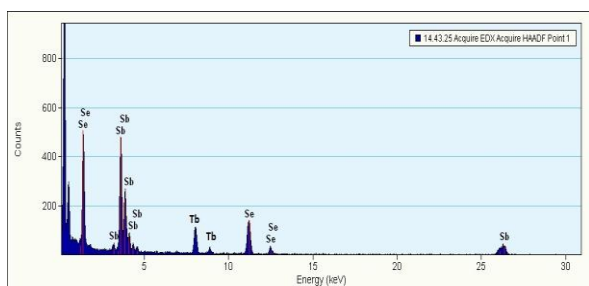


Figure 17. EDX patterns of $\text{Sb}_{2-x}\text{Tb}_x\text{Se}_3$ synthesized at 160°C and 24h.

The cell parameters of the synthesized materials were calculated from the XRD patterns. With increasing dopant content (x), the a , b , and c parameters for Tb^{3+} increase, as shown in Figure 3. The trend for lattice constants can be correlated to the effective ionic radii of the Tb^{3+} ions.

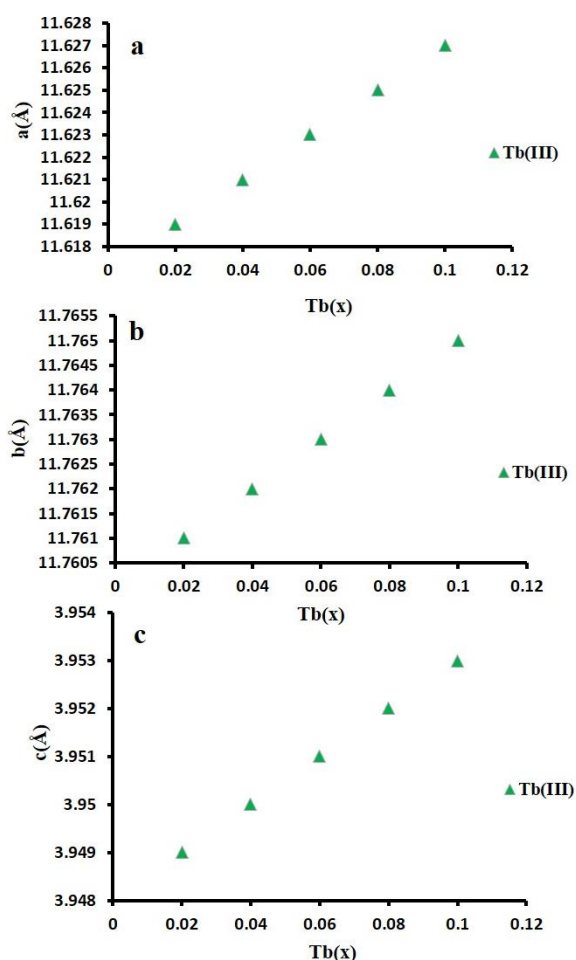


Figure 18. The a lattice constant (a) and b lattice constant (b) as well as c lattice constant (c) of $\text{Sb}_{2-x}\text{Tb}_x\text{Se}_3$ ($0 \leq x \leq 0.10$) dependent upon Tb^{3+} doping on Sb^{3+} sites.

Figure 4 shows SEM images of Sb_2Se_3 and Tb -doped Sb_2Se_3 . Doping of Tb^{3+} into the structure of Sb_2Se_3 changes the morphology from rods to particles. Figure 4a shows Sb_2Se_3 nanorods with thicknesses of 70–200 nm. The diameter of $\text{Sb}_{1.9}\text{Tb}_{0.1}\text{Se}_3$ particles is around 30 nm (Figure 4b).

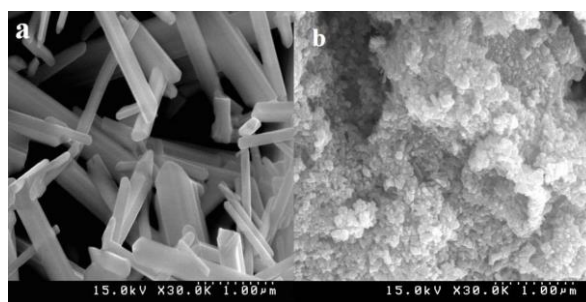


Figure 19. SEM image of Sb_2Se_3 (a), $\text{Sb}_{1.90}\text{Tb}_{0.1}\text{Se}_3$ nanoparticles (b) synthesized at 160°C and 24h.

The surface zone, normal pore measure, and normal pore volume of the $\text{Sb}_{1.90}\text{Tb}_{0.1}\text{Se}_3$ nanoparticles were assessed. Earlier to N_2 -physical adsorption estimations, the sample was degassed at 150°C for 120 min within the nitrogen environment. So, the particular surface range (SBET) of the gotten materials was decided with adsorption-desorption isotherms of N_2 at 77 K. The information is summarized in Table 1. It can be seen that the normal surface zone and pore breadth are approximately $1.84 \text{ m}^2 \text{ g}^{-1}$ and 20 nm.

Table 9. BET data for the fabricated samples.

Sample	BET surface area ($\text{m}^2 \text{ g}^{-1}$)	Pore diameter (nm)	Pore volume ($\text{cm}^3 \text{ g}^{-1}$)
S_1	1.84	20	0.0084

Sb_2Se_3 and its alloys are thermoelectric materials and have been investigated for direct conversion of thermal energy to electric energy as well as electronic refrigeration [30]. With the increase in the lanthanide concentration, the electrical resistivity of synthesized nanomaterials decreased obviously (Figure 5a). At room temperature, the electrical resistivity of pure Sb_2Se_3 was of the order of $0.2 \Omega \cdot \text{m}$ and in the case of Tb^{3+} -doped compounds the minimum value of electrical resistivity is $0.03 \Omega \cdot \text{m}$, respectively. The temperature dependence of the electrical resistivity for Tb -doped Sb_2Se_3 between 290–350 K is shown in Figure 5b. Electrical resistivity decreases linearly with temperature. As a result, the electrical conductance of Tb -doped Sb_2Se_3 materials is higher than pure Sb_2Se_3 at room temperature and increases with temperature.

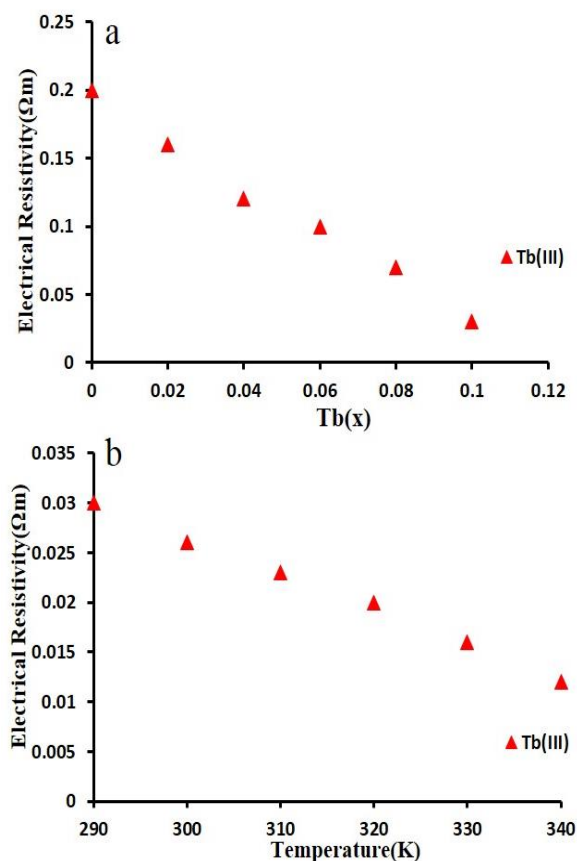


Figure 20. (a) Electrical resistivity and (b) thermoelectrical resistivity of $\text{Sb}_{2-x}\text{Tb}_x\text{Se}_3$ nanoparticles.

3.2. Photocatalytic study

To explore the perfect conditions of photocatalytic performance, the degradation process of Rhodamine B (RB) was examined under visible light irradiation by $\text{Tb}_x\text{Sb}_{2-x}\text{Se}_3$ with various mole fractions ($x = 0.00$ to $x = 0.1$). Figure 6 demonstrates the degradation percent of Rhodamine B over divergent Tb^{3+} -doped Sb_2Se_3 catalysts in 120 min of reaction. From Figure 6, it can be observed that the nanomaterials doped with proper content of Tb^{3+} ion had much enhanced photocatalytic performance than bare Sb_2Se_3 , principally the sample with a 0.1 molar ratio of Tb^{3+} , which displayed the best catalytic activity. The reason for the high photocatalytic activity of $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ can be described as follows: Normally, rare-earth cations can perform either as a recombination center or as a mediator of interfacial charge in the photocatalyst's crystalline structure [17, 18].

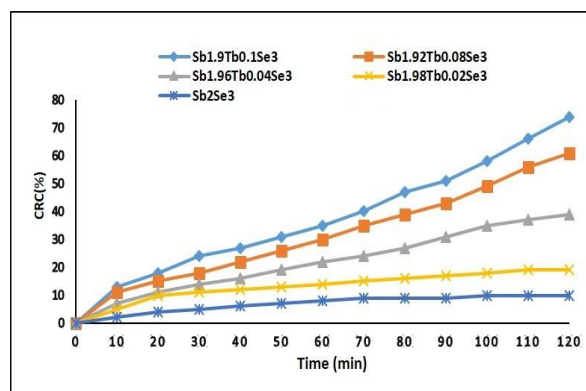


Figure 21. The effect of Tb^{3+} dopant content on the decolorization of 10 mg/L Rhodamine B (catalyst loading 1.0 g/L);

To properly explain the photocatalytic performance of the $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ samples and assess the realizable mechanism of the reaction, the UV-Vis absorption spectra of RB at different irradiation times for the photocatalytic process are exhibited in Figure 7. The decreasing concentration of RB in the time of the catalytic procedure is utilized to evaluate the potential of the catalyst.


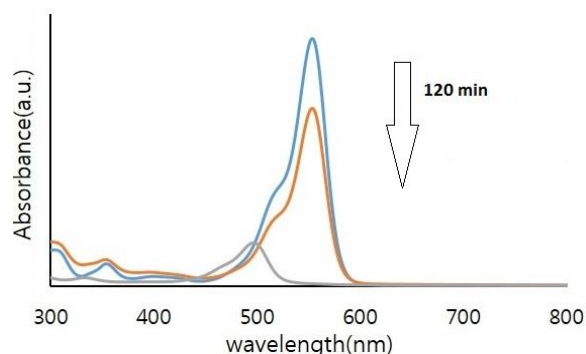


Figure 22. Adsorption and degradation of Rhodamine B under visible light irradiation using $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ nanoparticles.

The decolorization mechanism for the $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ is provided in Eqs 1-10.

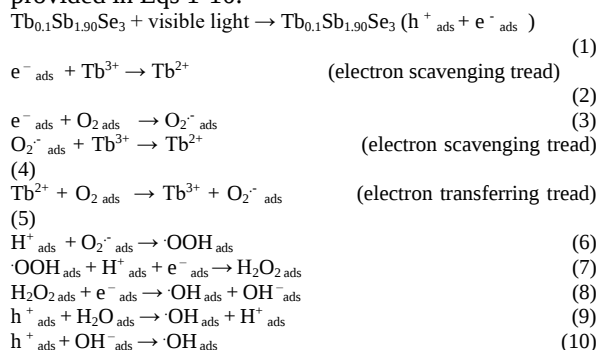

The reusability is one of the most substantial parts of a catalyst. Figure 8 displays the reusability assays of $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ catalyst in the degradation of Rhodamine B, during the 5 round tests under perfect conditions as 120 min for photocatalytic process, 10 mg/L of Rhodamine B, 1.0 g/L of $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ photocatalyst.

Following each degradation test, the catalyst was washed with distilled water and then dried at 70 °C for 2h and so utilized in the next run. As shown in Figure 8, $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ displayed outstanding chemical firmness without any significant decomposition or photo-corrosion during the 5 rounds of catalytic reaction which is an essential superior for empirical applications.

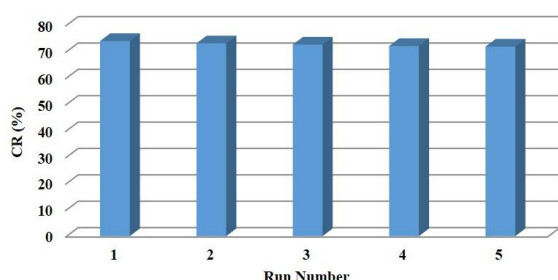


Figure 23. Reusability results of $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ in photocatalytic decolorization of 10 mg/L of Rhodamine B and 120 min for irradiation time.

To study the decolorization process's mechanism and to explore the main oxidative species, assays were carried out in the presence of proper scavengers of active species. As shown in Figure 9, adding oxalate (a scavenger of h^+_{VB}) results in the deduction of the decolorization percentage to 27.92%. In the case of benzoquinone (BQ) (a scavenger of superoxide radicals), the dye degradation was hindered extraordinarily. Adding t-BuOH (a scavenger of hydroxyl radicals) leads to a reduction of 47% in the decolorization percentage. Considering I^- (scavenger of the hole) it reaches 19.48 %, respectively. These results demonstrate that superoxide radicals and the h^+_{VB} were the principal oxidative species in decomposing dye structure. Nevertheless, the hydroxyl radicals also influence decolorization.

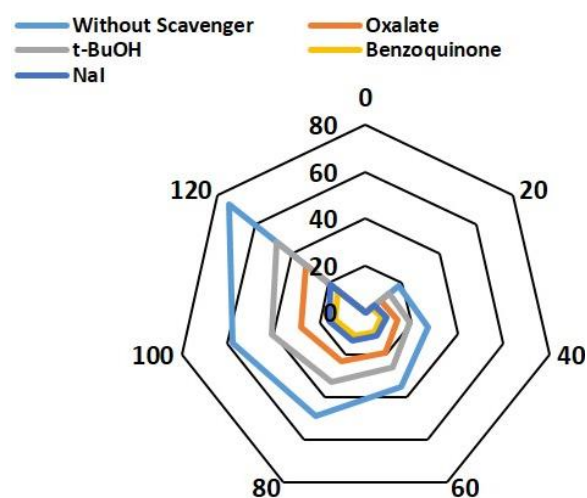


Figure 24. The effect of the addition of benzoquinone, butanol, I^- and oxalate ions on the decolorization of 10 mg/L RB ($\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ loading 1.0 g/L).

Conclusion

In this research, pure and Tb^{3+} -doped Sb_2Se_3 were prepared by a simple hydrothermal approach and were employed as photocatalysts under visible light irradiation for removal of Rhodamine B. XRD analysis displayed well crystalline cubic structure of Sb_2Se_3 . The substitution of Tb^{3+} ions into the Sb_2Se_3 lattice was validated by the EDS analysis. The surface morphology and size of the samples have obvious changes from rods to nanoparticles after incorporating Tb^{3+} into the lattice of Sb_2Se_3 . Results indicated that the decolorization efficiency of Tb^{3+} -doped Sb_2Se_3 was higher than pure Sb_2Se_3 , and degradation efficiency was affected by the content of Tb dopant in Sb_2Se_3 . The promoted decolorization efficiency was found in the presence of 10 % Tb^{3+} -doped Sb_2Se_3 particles. The color removal percentage of $\text{Tb}_{0.1}\text{Sb}_{1.90}\text{Se}_3$ and undoped Sb_2Se_3 was 77.15 and 11.37% after 120 min of treatment, respectively. Benzoquinone caused the highest negative effect on the photocatalysis of Rhodamine B. Generally, the application of Tb^{3+} -doped Sb_2Se_3 particles can be a promising and effective approach for the elimination of colored effluents.

Acknowledgment

This work is funded by Sayyed Jamaledin Asadabadi University Research Grant.

References

1. Khataee AR, Khataee A, Fathinia M, Hanifehpour Y, Joo SW. Kinetics and mechanism of enhanced photocatalytic activity under visible light using synthesized PrxCd1-xSe nanoparticles. *Industrial Engineering Chemistry Research*. 2013; 52: 13357–13369.
DOI: <https://doi.org/10.1021/ie402352g>
2. Hammabard N, Hanifehpour Y, Khomami B, Joo SW. Synthesis, characterization and photocatalytic performance of Yb-doped CdTe nanoparticles. *Materials Letters*. 2015; 145: 253-257.
DOI: <https://doi.org/10.1016/j.matlet.2015.01.074>
3. Tryk DA, Fujishima A, Honda K. Recent topics in photo electrochemistry: achievements and future prospects. *Electrochimica Acta*. 2000; 45: 2363-2376.
DOI: [https://doi.org/10.1016/S0013-4686\(00\)00337-6](https://doi.org/10.1016/S0013-4686(00)00337-6)
4. S. Ahmed, M.G. Rasul, W.N. Martens, R. Brown, M.A. Hashib, Heterogeneous photocatalytic degradation of phenols in wastewater: A review on current status and developments, *Desalination*. 261 (2010) 3–18.
DOI: <https://doi.org/10.1016/j.desal.2010.04.062>
5. Alemi A, Hanifehpour Y, Joo SW, Min BK. Synthesis of novel $\text{Ln}_x\text{Sb}_{2-x}\text{S}_3$ (Ln: Lu^{3+} , Ho^{3+} , Nd^{3+}) nanomaterials via co-reduction method and investigation of their physical properties. *Colloids and Surfaces A: Physicochemical Engineering Aspects*. 2011; 390: 142–148.
DOI: <https://doi.org/10.1016/j.colsurfa.2011.09.018>
6. Hanifehpour Y, Joo SW. Synthesis, characterization and sonophotocatalytic degradation of an azo dye on

- Europium doped cadmium selenide nanoparticles. *Nanochemistry Research*.2018; 3(2): 178-188.
DOI: <https://doi.org/10.22036/NCR.2018.02.007>
7. A. Khataee, S. Saadi, B. Vahid, S.W. Joo, B.-K. Min, Sonocatalytic degradation of Acid Blue 92 using sonochemically prepared samarium doped zinc oxide nanostructures, *Ultrason. Sonochem.* 29 (2016) 27–38.
DOI: <https://doi.org/10.1016/j.ultsonch.2015.07.026>
 8. C. Mastrovito, J.W. Lekse, J.A. Aitken, Rapid solid-state synthesis of binary group 15 chalcogenides using microwave irradiation. *J. Solid State Chem.* 180 (2007) 3262-3270.
DOI: <https://doi.org/10.1016/j.jssc.2007.09.001>
 9. X. Qiu, C. Burda, R. Fu, J. Zhu, et al., Heterostructured Bi₂Se₃ Nanowires with Periodic Phase Boundaries. *J Am Chem Soc.* 126 (2004) 16276-16277.
DOI: <https://doi.org/10.1021/ja045556r>
 10. H. Ji, X. Zhao, Y. Zhang, B. Lu B ,H. Ni, Solvothermal synthesis and thermoelectric properties of lanthanum contained Bi–Te and Bi–Se–Te alloys .*Mater Lett.* 59 (2005) 682-685.
DOI: <https://doi.org/10.1016/j.matlet.2004.11.008>
 11. P. Janíček, C. Drasar, P. Losták , J. Vejpravová, Transport, magnetic, optical and thermodynamic properties of Bi₂–xMnxSe₃ single crystals *Physica B.* 403(2008) 3553-3558.
DOI: <https://doi.org/10.1016/j.physb.2008.05.025>
 12. P. Lostak, C. Drasar, I. Klichova, T. Cernohorsky, Properties of Bi₂Se₃ single crystals doped with Fe atoms *Phys Status Solidi B.* 200(1997) 289-296.
DOI: [https://doi.org/10.1002/1521-3951\(199703\)200:1%3C289::AID-PSSB289%3E3.0.CO;2-8](https://doi.org/10.1002/1521-3951(199703)200:1%3C289::AID-PSSB289%3E3.0.CO;2-8)
 13. S. Augustin, E. Mathai, Growth, morphology, and microindentation analysis of Bi₂Se₃, Bi_{1.8}In_{0.2}Se₃, and Bi₂Se_{2.8}Te_{0.2} single crystals. *Mater Res Bull.*36 (2001) 2251-2261.
DOI: [https://doi.org/10.1016/S0025-5408\(01\)00717-6](https://doi.org/10.1016/S0025-5408(01)00717-6)
 14. N.S. Patil, A.M. Sargar, S.R. Mane, P.N. Bhosale, Growth mechanism and characterization of chemically grown Sb doped Bi₂Se₃ thin films *Appl Surf Sci.* 254(2007)5261-5265.
DOI: <https://doi.org/10.1016/j.apsusc.2008.02.084>
 15. P. Larson, R.L. Lambrecht, Electronic structure and magnetism in Bi₂Te₃, Bi₂Se₃, and Sb₂Te₃ doped with transition metals (Ti–Zn) *Phys Rev B.* 78(2008) 195207-195214.
DOI: <https://doi.org/10.1103/PhysRevB.78.195207>
 16. X. Gratens, S. Isber, S. Charar, C. Fau, M. Averous, *Phys Rev B.* 55(1997) 8075-8078.
DOI: <https://doi.org/10.1103/PhysRevB.55.8075>
 17. Khataee AR, Hanifehpour Y, Safarpour M, Hosseini M, Joo SW. Synthesis and characterization of Er xZn1–x Se nanoparticles: a novel visible light responsive photocatalyst . *Science of Advanced Materials.* 2013; 5: 1074–1082.
DOI: <https://doi.org/10.1166/sam.2013.1556>
 18. Y. Hanifehpour, B. Soltani, A.R. Amani-Ghadim, B. Hedayati, B. Khomami, S.W. Joo, Synthesis and characterization of samarium-doped ZnS nanoparticles: A novel visible light responsive photocatalyst, *Mater. Res. Bull.* 76 (2016) 411–421.
DOI: <https://doi.org/10.1016/j.materresbull.2015.12.035>